

Comparative evaluation of fracture resistance of primary anterior teeth restored with long dentine posts and teeth restored with short fiber posts: An in vitro study

Reham E.L. Ghazawy, Amira Badran*

Pediatric Dentistry and Dental Public Health, Faculty of Dentistry, Ain Shams University, Egypt

ARTICLE INFO

Article history:

Received 15 August 2017

Received in revised form

30 October 2017

Accepted 12 November 2017

Available online 5 December 2017

ABSTRACT

Background: Badly broken primary teeth that require pulp therapy present a high-risk of biomechanical failure due to the loss of tooth substance resulting from pre-existing decay and endodontic therapy itself. The introduction of Biological dentine posts offered an excellent alternative for restoring such teeth. The ideal post material should have physical and mechanical properties that are similar to those of dentine. Accordingly there is no such material other than dentine itself. Another concern in restoring endodontically treated primary teeth is the need to find a material that can resorb in a similar way to natural tooth structure as a part of the exfoliation process allowing normal eruption of permanent successors. The difficulty of finding such a material had urged Pedodontists to only use short posts in restoring badly broken primary anterior teeth which adversely affected the retention of the posts and resulted in a less favorable stress distribution along the post. The aim of the current study was to assess the effect of using long dentine posts on the fracture resistance of endodontically treated primary anterior teeth in comparison to primary anterior teeth restored with short fiber posts.

Methods: A sample of thirty primary anterior teeth was collected from the outpatient clinic of Pediatric Dentistry and Dental Public Health Department. Ten extracted premolars were also collected from the outpatient clinic of Oral and Maxillofacial Department. Both departments are at the Faculty of Dentistry, Ain Shams University. The roots of the premolars were used to prepare twenty dentine posts of a standardized shape and dimensions, using CNC milling machine. After receiving proper filing and endodontic radicular preparation, the primary teeth were divided into two groups (fifteen teeth in each group). The first group was restored with dentine posts of 5 mm length, and the second group was restored with fiber posts 3 mm in length. For both groups, fracture resistance testing was performed using universal testing machine.

Results: Mann-Whitney U test was used to compare between the two post types. Long dentine posts showed statistically significantly lower mean fracture resistance than short fiber posts.

Conclusion: Short fiber posts offered better fracture resistance when compared to long dentine posts.

© 2018 Faculty of Oral & Dental Medicine, Future University. Production and hosting by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

Maintenance of primary dentition in a healthy condition is important for the well-being of children. It ensures proper mastication, esthetics, phonetics, space-maintenance, and prevention of aberrant habits [1].

The partial or complete loss of coronal tooth structure in the primary dentition may occur due to dental caries or physical trauma [2,3]. Severe early childhood caries is a devastating condition for both the child undergoing dental treatment and the concerned parents. It is also challenging for pediatric dentists to restore badly broken down teeth [4–6]. The goal of dental treatment is to restore the lost tooth structure. Its early loss may result in reduced masticatory efficiency and loss of vertical dimension. Furthermore, development of parafunctional habits such as tongue thrusting, speech problems and esthetic-functional problems such

* Corresponding author.

E-mail address: dr.amirabdrn@yahoo.com (A. Badran).

Peer review under responsibility of Faculty of Oral & Dental Medicine, Future University.

as malocclusion and space loss. Altogether, tooth loss may cause psychological burdens that can interfere in the personality and behavioral development of the child [7,8].

Several attempts have been made by clinicians to restore grossly decayed anterior primary teeth with innovative root canal retentive post and core systems so that the primary teeth are retained until they are replaced by permanent teeth. There are several types of root canal posts available for use in pediatric restorative dentistry, including pre-manufactured orthodontic wire in “ α ” or “ γ ” forms [4], omega forms [9], metallic posts with macro-retention [10], short posts with composite resin [11], and polyethylene ribbon posts [4]. In addition, newer post systems such as carbon fiber, glass fiber, and zirconium oxide posts, offer excellent features including biocompatibility, fatigue, and corrosion resistance and have mechanical properties similar to dentin [6,12]. Although these restorative methods aim at recovering the oral function, yet they do not allow subsequent smooth transition to permanent teeth, or physiological root resorption of primary teeth [13].

The introduction of dentin posts in few reported cases has shown promising outcomes [14–16]. These posts can be naturally resorbed as part of the process of exfoliation of the primary teeth and might be considered an alternative for rehabilitation in pediatric dentistry. This could be an advantage when compared to resin or metallic posts [17]. Dentin posts can also be expected to have physical properties similar to those of the teeth such as modulus of elasticity, compressive strength and thermal expansion [16]. However, there is deficiency of evidence in literature concerning the use of dentin posts in primary teeth, and in spite that it has been suggested that post length in permanent teeth must be at least equal to the crown height or two-thirds of the root length to facilitate stress distribution and provide resistance to occlusal forces. Yet there is no evidence of using long posts in primary teeth due to the physiological resorption that primary teeth undergo. Accordingly, the current study sought to investigate the fracture resistance of primary anterior teeth restored with long dentine posts that would undergo natural resorption, to investigate the effect of increasing the length of the posts on the strength of pulp treated primary anterior teeth.

2. Materials and methods

Thirty primary anterior teeth were collected from the outpatient clinic of Pediatric Dentistry and Dental Public Health Department, Faculty of Dentistry, Ain Shams University. At least two thirds of the root length should be present, the roots were caries free and no previous endodontic treatment was performed in these teeth [18]. Ten extracted premolars were also collected from the outpatient clinic of Oral and Maxillofacial Department, Faculty of Dentistry, Ain Shams University. They were freshly extracted for orthodontic reasons. The roots of the premolars were used to prepare twenty dentin posts of a standardized shape and dimensions, using Computer Numerical Control (CNC) milling machine (Centroid, USA) (Figs. 1 and 2) [16]. The prepared dentin posts were all autoclaved at 121 °C for 20 min before use to insure all biosecurity standards for teeth disinfection and to simulate clinical condition [19]. The fiber posts used in this study were the red color-coded Easy posts (Dentsply, Maillefer, USA). They were silanized using silane (Ultradent Inc. USA) according to the manufacturer's instructions.

The thirty primary anterior teeth were cross-sectioned 1 mm above the cement-enamel junction (CEJ). Each root canal was filed with MANI Hedstrom endodontic Files up to size 40, irrigated with normal saline solution and then dried with paper points. Metapex (META-BIOMED Co. LTD, Korea) was then injected into the canal space. The teeth were divided into two groups: Group [1] for dentin posts and Group [2] for fiber posts. For group 1, a plugger with a



Fig. 1. Milling half of premolar root to generate biological dentine posts.



Fig. 2. Biological Dentine posts.

stopper adjusted at 6 mm was used to condense the Metapex. This was done to confirm that 6 mm of the canal space coronally was left free from the Metapex. For group 2, 4 mm was left free from the Metapex. Glass ionomer lining cement (GC Equia, Tokyo, Japan) was then inserted into the canal space and adapted with the same plugger. Excess glass ionomer cement was removed so that the post space inside the root canal was 5 mm for the dentin posts and 3 mm for the fiber posts [20,21].

The dentin posts were cut so as to obtain the length of 8 mm for each post. Five millimeters of each post was inserted inside the root canal and cemented with self-adhesive resin cement (GC G-cem, Tokyo, Japan) leaving 3 mm coronally for crown build up. As for the second group, fiber posts were cut so as to obtain 6 mm. Only 3 mm of each fiber post was inserted inside the root canal and cemented, 3 mm were left coronally for crown building up. For both groups,

crown build up was performed using celluloid strip crowns and Flowable composite resin (Filtek Z350 XT) (Fig. 3) [20]. All the specimens were mounted in self-cured acrylic resin and thermo-cycled for 500 cycles; each cycle included immersion for 30 s into the hot bath at $55 \pm 1^\circ\text{C}$ followed by immersion for same time into the cold bath at $5 \pm 1^\circ\text{C}$ with 5 s delay between the hot and cold baths to simulate the temperature dynamics in the oral environment and hence increasing the accuracy of results [21,22].

The fracture resistance was measured using the Universal Testing Machine. Each specimen was held in a specially constructed attachment that was fixed to the lower compartment of the machine so that the specimen's inclination was 45° . A specially constructed load applicator in the form of metallic rod with a ball end 1 mm in diameter, was fixed to the upper compartment of the machine so that the dislodging force was at the junction between the incisal and middle thirds of the crown (Fig. 4). The specimens were loaded at a cross head speed of 1 mm/min. The values obtained at fracture were recorded in Newtons.

2.1. Statistical analysis

Numerical data were explored for normality by checking the data distribution and using Kolmogorov-Smirnov and Shapiro-Wilk tests. Data showed non-parametric (non-normal) distribution. Data



Fig. 3. Specimens after crown building-up.



Fig. 4. Fracture resistance testing.

were represented as mean, standard deviation (SD), median, range and 95% Confidence interval (95% CI) values.

Mann-Whitney *U* test was used to compare between the two post types (Table 1, Fig. 5).

The significance level was set at $P \leq 0.05$. Statistical analysis was performed with IBM¹ SPSS² Statistics Version 20 for Windows.

3. Results

Biological long post showed statistically significantly lower mean fracture resistance than fiber post.

4. Discussion

Dental caries and trauma are the most common causes of crown destruction in primary anterior teeth [23]. For many years, extraction was the treatment of choice for these badly broken teeth. However, early loss can cause a number of disturbances as loss of space, phonetic alterations, impaired mastication and psychological problems affecting the self-esteem of the child [10,14]. Satisfactory rehabilitation treatment is still a challenge [18]. Gaining intra-canal retention using posts in primary anterior teeth is more complicated than in permanent teeth because the primary teeth have to exfoliate normally giving a way to their permanent successors to erupt in undeflected positions [24]. Accordingly, the standard practice in pediatric dentistry was to use short posts that never exceeded 3 mm length inside the canal [4,8,21]. Other much needed requirements of intra-canal posts for primary anterior teeth are biocompatibility, availability, ease of application, esthetics and ability to withstand masticatory forces [24].

Dentin posts turned the scale as they can be resorbed as a part of the shedding process. They also have all the desired characteristics discussed above and an additional advantage of being inexpensive [24]. Previously, the dentin posts have been prepared using primary root dentin [14,25,26] yet the limited availability and difficulty of finding primary root dentin free from resorption, urged pedodontists to use premolar root dentin that is widely available, being the most common tooth extracted for orthodontic reasons. Another advantage of using the premolar root is the ease of finding them in sound form [24]. One of the limitations of using biologic restorations is preoperative preparation, such as sterilization and preparation of natural tooth to make dentin post/post and core/shell crown. But, these steps can be performed by dental auxiliaries as well, and the dentist does not need to waste time for this. Some parents may find this technique unacceptable. However, it is the pedodontist role to reassure them and inform them about the harmless nature of this restorative modality [24].

An ideal post system should exhibit fracture resistance higher than the average masticatory forces [27]. It has been suggested that post length in permanent teeth must be at least equal to the crown height or two-thirds of the root length to facilitate stress distribution and provide resistance to occlusal forces leaving at least 4 mm of gutta-percha. In contrast, increasing post length could decrease the root strength [28].

As for primary teeth, no consensus exists concerning the proper length for posts, the influence of long posts in primary teeth needs to be determined. Accordingly, the current study assessed the effect of using long dentin posts on the fracture resistance of endodontically treated primary anterior teeth in comparison to primary anterior teeth restored with short fiber posts.

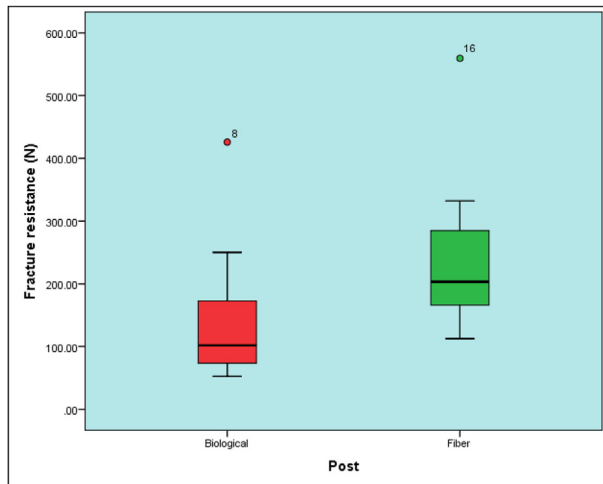
Fracture resistance is one of the main desirable characteristics of

¹ IBM Corporation, NY, USA.

² SPSS, Inc., an IBM Company.

Table 1Descriptive statistics and results of Mann-Whitney *U* test for comparison between fracture resistance values (N) of the two post types.

Post type	Mean	SD	Median	Minimum	Maximum	95% CI		P-value
						Lower bound	Upper bound	
Biological	145.8	112.3	101.9	52.5	425.9	70.4	221.2	0.029 ^a
Fiber	239.4	130.8	203.3	112.4	559.3	145.8	333.0	

^a Significant at $P \leq 0.05$.**Fig. 5.** Box plot representing fracture resistance of the two post types (Circles represent outliers).

restoration materials, especially during mastication and the most important factor in achieving a durable restoration [29]. In addition, post placement has a significant influence on the final fracture resistance of the restored teeth [30]. Unfortunately, there is scarcity in studies measuring the fracture resistance of posts in primary teeth specially dentin posts. In 2014, Baghalian et al. [20] tested the fracture resistance of four different posts used in the restoration of severely decayed primary incisors (Intact glass fiber posts, splinted glass fiber posts, composite resin posts, and orthodontic “γ” wire posts). They found out that there was no significant difference between any of the groups. Seraj et al. (2015) [21] compared the fracture resistance of three types of posts in restoration of severely damaged primary anterior teeth. Group 1: Customized quartz fiber post, Group 2: Composite resin post and Group 3: Prefabricated glass fiber posts. It was concluded that all three types of studied posts could be successfully used to restore badly broken down primary anterior teeth.

In spite of being biocompatible and having similar physical properties to those of the teeth, surprisingly in the current study the long biological dentin posts showed statistically significant lower mean fracture resistance than fiber posts. These results disagreed with a number of studies that assessed the fracture resistance of biological dentin posts. Unfortunately, most of these studies were carried out on permanent anterior teeth and there is a deficiency in literature regarding primary teeth. Kathuria et al. (2011) [16] and Ambica et al. (2013) [31] found that permanent teeth restored with dentin posts exhibited better fracture resistance than those restored with fiber posts. The results in the current study may be attributed to the histological difference between primary and permanent teeth which needs further investigations. As well as, the vast variations that could be present between the premolars from which the posts were milled, and this explains the diversity in the fracture resistance readings of the dentin post specimens. Besides the limitation of the small sample size that was

due to the difficulty in finding primary anterior teeth with at least two thirds of the root present.

5. Conclusion

From the above discussion, it becomes clear that, there is a continuous need for evaluation of various post systems for primary teeth to make evidence-based decision. Currently, the evidence is lacking to provide any recommendation about the possibility of using long dentin posts alternatively to other short posts systems for primary teeth. Yet, the present study might provide a strong base for further trials in this field advocating larger sample size and a well-defined and standardized methodology to eliminate variations and diversities in the prepared biological dentin posts.

References

- [1] Jain M, Singla S, Bhushan BAK, Kumar S, Bhushan A. Esthetic rehabilitation of anterior primary teeth using polyethylene fiber with two different approaches. *J Indian Soc Pedod Prev Dent* 2011;29(4):327–32.
- [2] Fried I, Erickson P. Anterior tooth trauma in the primary dentition: incidence, classification, treatment methods, and sequelae: a review of the literature. *ASDC J Dent Child* 1995;62:256–61.
- [3] Aminabadi NA, Farahani RMZ. The efficacy of a modified omega wire extension for the treatment of severely damaged primary anterior teeth. *J Clin Pediatr Dent* 2009;33(4):283–8.
- [4] Vieira CL, Ribeiro CC. Polyethylene fiber tape used as a post and core in decayed primary anterior teeth: a treatment option. *J Clin Pediatr Dent* 2001;26:1–4.
- [5] Sharaf AA. The application of fiber core posts in restoring badly destroyed primary incisors. *J Clin Pediatr Dent* 2002;26:217–24.
- [6] Gujjar KR, Indushekar KR. Comparison of the retentive strength of 3 different posts in restoring badly broken primary maxillary incisors. *J Dent Child* 2010;77:17–24.
- [7] Ripa LW. Nursing caries: a comprehensive review. *Pediatr Dent* 1988;10(4):268–82.
- [8] Verma L, Passi S. Glass fibre-reinforced composite post and core used in decayed primary anterior teeth: a case report. *Case Reports in Dentistry*. 2011. p. 1–4.
- [9] Mortada A, King NM. A simplified technique for the restoration of severely mutilated primary anterior teeth. *J Clin Pediatr Dent* 2004;28:187–92.
- [10] Wanderley MT, Ferreira SL, Rodrigues CR, Rodrigues FLE. Primary anterior tooth restoration using posts with macroretentive elements. *Quintessence Int* 1999;30:432–6.
- [11] Mendes FM, De Benedetto MS, Del Conte Zardetto CG, Wanderley MT, Correa MS. Resin composite restoration in primary anterior teeth using short-post technique and strip crowns: a case report. *Quintessence Int* 2004;35:689–92.
- [12] Mitsui FH, Marchi GM, Pimenta LA, Ferraresi PM. In vitro study of fracture resistance of bovine roots using different intraradicular post systems. *Quintessence Int* 2004;35:612–6.
- [13] Mizutani T, Nakayama A, Iwasaki H, Miyazawa H. Suitability of polymers as screw post materials in primary teeth: an in vitro study. *Eur J Paediatr Dent* 2012;13:19–24.
- [14] Ramires-Romito AC, Wanderley MT, Oliveira MD, Imparato JC, Correa MS. Biologic restoration of primary anterior teeth. *Quintessence Int* 2000;31:405–11.
- [15] De Alcântara CE, Corrêa-Faria P, Vasconcellos WA, Ramos-Jorge ML. Combined technique with dentin post reinforcement and original fragment reattachment for the esthetic recovery of a fractured anterior tooth: a case report. *Dent Traumatology* 2010;26:447–50.
- [16] Kathuria A, Kavitha M, Khetarpal S. Ex vivo fracture resistance of endodontically treated maxillary central incisors restored with fiber-reinforced composite posts and experimental dentin posts. *J Conservative Dent* 2011;14(4):401–5.
- [17] Pinheiro SL, Bönecker MJS, Duarte DA, Imparato JCP, Oda M. Bond strength analysis of intracanal posts used in anterior primary teeth: an in vitro study.

- J Clin Pediatr Dent 2006;31(1):32–4.
- [18] Alves FBT, Vieira RS. Effects of eugenol and non-eugenol endodontic fillers on short post retention, in primary anterior teeth: an in vitro study. J Clin Pediatr Dent 2004;29(3):211–4.
 - [19] Swarupa CH, Sajjan GS, Bhupathiraju VL, Anwarullah A, Sashikanth YV. Biological dentin post for intra radicular rehabilitation of a fractured anterior tooth. J Clin Diagnostic Res 2014;8(2):242–3.
 - [20] Baghalian A, Ranjpour M, Hooshmand T, Herman NG, Ebrahimi A. Comparison of fracture resistance in post restorations in primary maxillary incisors. Eur J Paediatr Dent 2014;15(3):313–6.
 - [21] Seraj B, Ghadimi S, Estaki Z, Fatemi M. Fracture resistance of three different posts in restoration of severely damaged primary anterior teeth: an in-vitro study. Dent Res J 2015;12(4):372–8.
 - [22] Navimipour EJ, Chaharom MEE, Oskoe PA, Mohammadi N, Bahari M, Firouzmandi M. Fracture resistance of endodontically-treated maxillary premolars restored with composite resin along with glass fiber insertion in different positions. J Dent Res Dent Clin Dent Prospects 2012;6(4):125–30.
 - [23] Sheiham A. Strategies for promoting oral health care. Rev Bras Saude Coletiva 2001;2:7–24.
 - [24] Mittal N, Bhatia HP, Haider K. Methods of intracanal reinforcement in primary anterior teeth- Assessing the outcomes through a systematic literature review. Int J Clin Pediatr Dent 2015;8(1):48–54.
 - [25] Grewal N, Seth R. Comparative in vivo evaluation of restoring severely mutilated primary anterior teeth with biological post and crown preparation and reinforced composite restoration. J Indian Soc Pedod Prev Dent 2008; 141–8.
 - [26] Mittal NP. Restoring the smile: inexpensive biologic restorations. J Dent Res (Ishan) 2014;11(3):415–21.
 - [27] Raygot CG, Chai J, Jameson DL. Fracture resistance and primary failure mode of endodontically treated teeth restored with a carbon fiber-reinforced resin post system in vitro. Int J Prosthodont 2001;14(2):141–5.
 - [28] Chuang SF, Yaman P, Herrero A, Dennison JB, Chang CH. Influence of post material and length on endodontically treated incisors: an in-vitro and finite element study. J Prosthet Dent 2010;104(6):379–88.
 - [29] Samaha AE, EL-Shabrawy S, EL-Meligy O, Hashem R. Clinical and laboratory evaluation of two different types of the post system in restoring destructured primary anterior teeth. Egypt Dent J 2005;51:1159–77.
 - [30] Mangold JT, Kern M. Influence of glass-fiber posts on the fracture resistance and failure pattern of endodontically treated premolars with varying substance loss: an in vitro study. J Prosthet Dent 2011;105(6):387–93.
 - [31] Ambica K, Mahendran K, Talwar S, Verma M, Padmini G, Periasamy R. Comparative evaluation of fracture resistance under static and fatigue loading of endodontically treated teeth restored with carbon fiber posts, glass fiber posts, and an experimental dentin post system: an in vitro study. J Endod 2013;39(1):96–100.